

Selective hydrogenation of citral over Au-based bimetallic catalysts in supercritical carbon dioxide

LIU RuiXia & ZHAO FengYu*

State Key Laboratory of Electroanalytical Chemistry; Laboratory of Green Chemistry and Process, Changchun Institute of Applied Chemistry, Chinese Academy of Sciences, Changchun 130022, China

Received March 19, 2010; accepted April 21, 2010

Selective hydrogenation of citral was investigated over Au-based bimetallic catalysts in the environmentally benign supercritical carbon dioxide (scCO₂) medium. The catalytic performances were different in citral hydrogenation when Pd or Ru was mixed (physically and chemically) with Au. Compared with the corresponding monometallic catalyst, the total conversion and the selectivity to citronellal (CAL) were significantly enhanced over TiO₂ supported Pd and Au bimetallic catalysts (physically and chemically mixed); however, the conversion and selectivity did not change when Ru was physically mixed with Au catalyst compared to the monometallic Ru/TiO₂, and the chemically mixed Ru-Au/TiO₂ catalyst did not show any activity. The effect of CO₂ pressure on the conversion of citral and product selectivity was significantly different over the Au/TiO₂, Pd-Au/TiO₂, and Pd/TiO₂ catalysts. It was assumed to be ascribed to the difference in the interactions between Au, Pd nanoparticles and CO₂ under different CO₂ pressures.

supercritical CO₂, citral, hydrogenation, bimetallic catalysts, synergistic effects

1 Introduction

Supercritical carbon dioxide (scCO₂) as a benign medium has received much attention in chemistry and reaction engineering, because it satisfies several green chemistry and engineering principles such as pollution prevention, lower toxicity, and use of an “abundantly available” resource with no increase in environmental burden and easy separation from products through depressurization [1, 2]. In addition, CO₂ is chemically inert toward the substrates in most cases. Therefore, scCO₂ is regarded as a particular promising solvent for chemical reactions, especially, for the heterogeneous catalytic reactions involving gases such as H₂ and O₂, due to its complete miscibility with these gases, and the coke and products absorbed on the surface of catalysts can be removed by scCO₂, prolonging the life of the catalysts

[3]. As reported, the tunable solvent properties of scCO₂ make it possible to adjust the reaction rate and product selectivity through changing pressure [4–6].

Recently, the use of Au in heterogeneous catalysis has attracted much attention in controlling product selectivity in hydrogenation reactions such as selective hydrogenation of unsaturated ketones [7], acrolein [8] and 1,3-butadiene [9], although the overall rate of hydrogenation reaction over Au catalysts is much lower compared with that over conventional Pd, Pt and Ni catalysts [10–14]. For example, it was reported that Au/TiO₂ was much less active than Pt/TiO₂, but it was highly selective to produce crotyl alcohol in hydrogenation of crotonaldehyde [15]. However, practical applications require the total activity of Au to be improved with the specific selectivity unchanged. Many attempts have been made to develop efficient Au-based catalyst, for example, alloying Au with other components to form bimetallic catalysts was an efficient way, as these bimetallic catalysts often show highly improved activity due to the geometric

*Corresponding author (email: zhaofy@ciac.jl.cn)

and electronic effects [16, 17]. The Au-Pd alloy catalysts showed superior activities compared to the monometallic Pd or Au nanoparticles in hydrogenation of aromatic compounds [18, 19], acetylene [20, 21], and hydrodehalogenation reactions [22–24]. Furthermore, it was reported that the incorporation of Au with Pd- or Pt-based catalysts could improve the resistance toward deactivation in hydrodesulfurization [25] and hydrogenation reactions [26] through preventing the formation of undesired carbon and/or CO deposits covering or adsorbing on active metallic surface. In our previous work, the TiO₂-supported physically and chemically mixed Au and Pd bimetallic catalysts showed significant synergetic effect on the reaction rate and the selectivity of citronellal during hydrogenation of citral in scCO₂. Compared with *n*-hexane solvent, the overall reaction rate was enhanced due to high H₂ solubility and fast mass transfer rate in scCO₂, and the selectivity to citronellal was improved due to the molecular interaction between CO₂ and the reactant [27].

The above results have stimulated us to conduct a further study on the reaction features of selective hydrogenation of citral over the Au-based catalysts in scCO₂. Our intention is to investigate the potentiality of Au in the Pd-Au/TiO₂ bimetallic catalyst and the effect of CO₂ pressure on the product selectivity and conversion in scCO₂.

2 Experimental

2.1 Catalyst preparation

Several supported monometallic and bimetallic catalysts were prepared using an anatase TiO₂ (surface area of 120 m² g⁻¹) support supplied from Nanjing Haitai Nanomaterial Co. 1 wt% Au/TiO₂ monometallic catalyst was prepared by deposition-precipitation as reported in our previous work [27]. Typically, an aqueous solution of HAuCl₄ (Sinopharm Chemical Reagent Co., Ltd.) was prepared and its pH was adjusted to 10 with 5 M NaOH solution. The TiO₂ support was added to this solution with vigorous stirring and the

resulting suspension was aged at room temperature for 2 h with stirring. An aqueous solution of NaBH₄ was dropwise added into this suspension with vigorous stirring. The NaBH₄ aqueous solution was prepared in an ice water bath, and the molar ratio of NaBH₄ to Au is 10. Upon the addition of the NaBH₄ solution, the color of the mixture turned to pink purple, indicating the reduction of the auric ions. After aging for 3 h, the solid materials were separated by centrifugation at 10000 rpm. The supernatant was clear and colorless. The precipitates obtained were washed thoroughly with deionized water and absolute ethanol and separated again by centrifugation. The washing and the centrifugation were repeated four times. Then, the solid materials were dried in a vacuum oven at 80 °C overnight.

1 wt% Pd/TiO₂ and 1 wt% Ru/TiO₂ catalysts were prepared by a wet impregnation method. A precursor PdCl₂ (Shanghai Reagent Co.) was dissolved into an HCl solution and this PdCl₂ solution was diluted by deionized water. The support TiO₂ was added to this solution and the resulting slurry was vigorously stirred for 24 h at room temperature. After that, an ice cooled aqueous solution of NaBH₄ was added dropwise into this suspension with vigorous stirring. Upon the addition of the NaBH₄ solution, the color of the mixture turned gray, indicating the reduction of the palladium ions. After aging for 3 h, the solid materials were separated, washed, and dried in the same manner as described above for the Au/TiO₂ samples. Ru/TiO₂ catalyst was prepared with the same procedure except that the aqueous solution of RuCl₃·1.8H₂O (Aldrich) was used directly as a precursor without being dissolved in the HCl solution.

Bimetallic 0.5 wt%Pd-0.5 wt%Au/TiO₂ catalyst was prepared by co-impregnation method and reduced by NaBH₄ in similar procedures as used for the monometallic Pd/TiO₂ catalyst.

2.2 Activity test

The catalytic performance of the catalysts listed in Table 1

Table 1 Results of hydrogenation of citral over various TiO₂-supported Pd, Ru, and Au catalysts in scCO₂^{a)}

Entry	Catalyst	Time (h)	Conversion (%)	Selectivity (%)					
				DCAL	CAL	COL	G & N	IOL	others
1	Au/TiO ₂	4	6	8	70	3	16	3	0
2	Pd/TiO ₂	4	27	4	78	4	8	5	1
3	Ru/TiO ₂	4	15	8	61	5	22	3	2
4	Pd/TiO ₂ +Au/TiO ₂	1	69	4	90	1	4	1	0
5	Ru/TiO ₂ +Au/TiO ₂	4	16	6	57	4	23	3	8
6	Pd-Au/TiO ₂	4	51	13	61	4	2	21	0
7	Pd-Au/TiO ₂ ^{b)}	4	49	10	62	2	1	25	0

a) Reaction conditions: citral, 2 mmol; H₂ 4 MPa; CO₂ 8 MPa; 80 °C, catalyst weight 25 mg for monometallic catalysts, 50 mg for bimetallic catalysts, 25 mg for each physically mixed catalyst. The total metal loading of the catalysts used was 1 wt%, and each metal is 0.5 wt% in the bimetallic catalysts. b) is the recycling of the catalyst used in entry 6.

was tested for the selective hydrogenation of citral. The reaction runs were carried out in a stainless steel batch reactor (50 cm³). Certain amounts of citral and the catalysts were added into the reactor and the reactor was sealed and flushed with 2 MPa CO₂ at least three times. Then, the reactor was heated up to 80 °C and introduced with 4 MPa H₂ first and then the desired pressure CO₂ with a high-pressure liquid pump. The reaction was started with a continuous agitation at a speed of 800 rpm, where the mass transfer resistance was neglected, as confirmed in our previous work [28]. At the end of the reaction, the reactor was cooled to room temperature and the gases (H₂ and CO₂) were vented. Finally, the reaction mixture was extracted with *n*-hexane. The resulting solutions were analyzed with gas chromatography (GC-Shimadza-14C, FID, Capillary column Rtx-Wax 30 m 0.53 mm 0.25 mm) and gas chromatography/mass spectrometry (GC/MS, Agilent 5890).

3 Results and discussion


3.1 Catalytic performance of the TiO₂-supported metallic catalysts

The lattice of Pd and Au is similar. Au and Pd both have a face-centered-cubic structure and these two components are completely miscible over the entire range, while Au and Ru are essentially completely immiscible in the bulk, and the crystal structures of them are different, with ruthenium having a hexagonal-close-packed structure [29]. In this work, Pd and Ru were chosen to mix with Au, forming bimetallic catalysts, and different catalytic performances were expected.

The catalytic performances of the TiO₂-supported Pd, Ru, and Au catalysts were evaluated in selective hydrogenation

of citral in scCO₂. Citral hydrogenation is a significant reaction in the flavor, fragrance and pharmaceutical industries. The hydrogenation of citral is a complex reaction with various products such as citronellal (CAL), citronellol (COL), geraniol & nerol (G & N), menthol (MOL) and others shown in Scheme 1. Thus, it was often selected as a model reaction to test the performance of catalysts [30]. The hydrogenation results obtained are listed in Table 1.

The monometallic Au/TiO₂ was even less active, giving 6% conversion of citral and 70% selectivity of CAL, which was produced from hydrogenation of conjugated C=C bond (Table 1, entry 1). Pd/TiO₂ and Ru/TiO₂ were slightly more active than Au/TiO₂ catalyst, giving 27% and 15% conversion of citral, which are three times and twice as high as that over 1 wt% Au/TiO₂ under the same conditions, respectively. The difference in the total conversion of citral was ascribed to the capacity of hydrogen dissociation over the above active metal components. The selectivity to CAL was 78% for Pd/TiO₂ catalyst, which was higher than that for Ru/TiO₂ (61%). When the same quantities of Au/TiO₂ and Pd/TiO₂ were physically mixed and used for the reaction (Table 1, entry 4), the conversion of citral hydrogenation for 1 h was enhanced sharply to 69%, and the selectivity to CAL was increased to 90%. The synergistic effect and hydrogen spillover over the bimetallic catalysts were confirmed to be responsible for the enhancement in conversion and selectivity as reported in our previous work [27]. By contrast, the conversion and product selectivity did not change so much for the physically mixed Ru/TiO₂ and Au/TiO₂ catalysts compared with the monometallic Ru/TiO₂. The chemically mixed Ru-Au/TiO₂ bimetallic catalysts were almost inert in citral hydrogenation under the conditions used (the results were not given). However, the chemically mixed Pd-Au/TiO₂ bimetallic catalyst presented a large

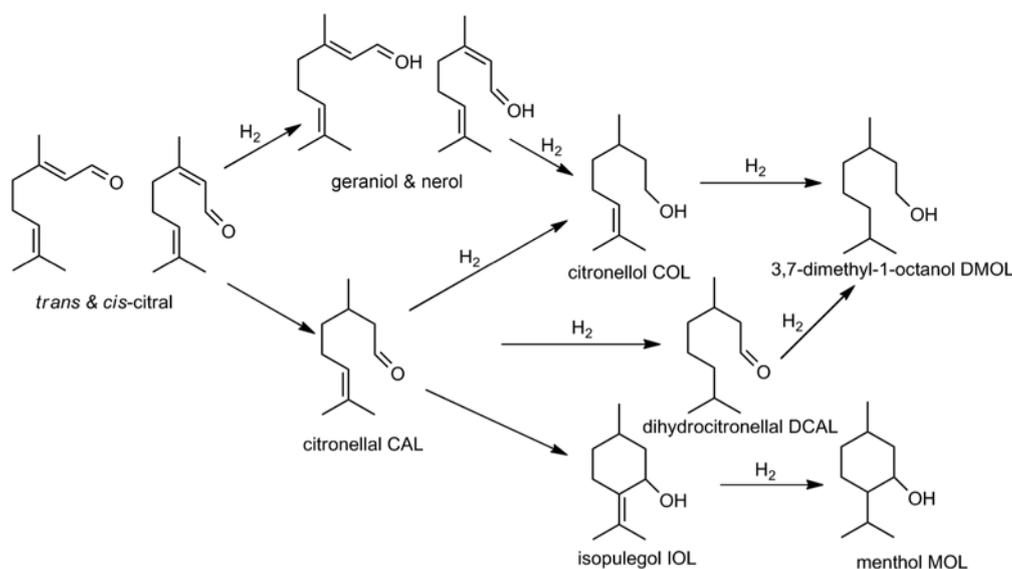

Scheme 1 Network of citral hydrogenation.

conversion (51%), which is eight times higher than that of monometallic Au/TiO₂, while the selectivity to CAL decreased to 61%, along with an increase in the selectivity to DCAL and isopulegol (IOL). It suggested that the catalytic performance depended on the nature of metal atoms on the surface of the catalysts (physically and chemically mixed). The recycling of bimetallic Pd-Au/TiO₂ catalyst was also investigated (Table 1, entries 6 and 7). Compared with the results for the first run (Table 1, entry 6), the conversion of citral and product selectivity did not change in the second run (Table 1, entry 7). The particle size of bimetallic Pd-Au/TiO₂ catalyst after the second run was almost unchanged, being about 1–2 nm, similar to the fresh one as shown in Figure 1.

3.2 Effect of CO₂ pressure

Figure 2 shows the effect of CO₂ pressure on the conversion and product selectivity of citral hydrogenation over bimetallic Pd-Au/TiO₂ and physical mixture of Au/TiO₂ and Pd/TiO₂ catalysts in the presence of 4 MPa H₂ at 80 °C, respectively. For the bimetallic Pd-Au/TiO₂ catalyst, the total conversion of citral increased from 51% to 72% when the CO₂ pressure changed from 6 to 12 MPa, but it decreased sharply when CO₂ pressure was above 12 MPa. With respect to the product selectivity, in the subcritical region (6 MPa CO₂) the selectivity to CAL was 61%, and it was around 55% almost

independent on CO₂ pressure in the supercritical region. CO₂ pressure showed different effects over the physical mixture Au/TiO₂ and Pd/TiO₂ catalysts. The conversion decreased gradually from 56% to 40% with CO₂ pressure in the range investigated, and the selectivity of citronellal increased from ~62% to ~73%.

For comparison, the effects of CO₂ pressure on the monometallic Pd/TiO₂ and Au/TiO₂ catalysts were also investigated under the same conditions, and the results are shown in Figures 3(a) and (b). A strong influence of CO₂ pressure has been observed on the conversion and product selectivity. For the monometallic Pd/TiO₂ catalyst, the conversion increased from 54% to 68% and the selectivity of CAL did not change as the CO₂ pressure changed from 6 to 8 MPa, but the conversion decreased significantly from 68% to 25% when CO₂ pressure was enhanced from 8 to 14 MPa. Meanwhile the selectivity of CAL increased from 51% to 74%, along with a decrease in the selectivity of DCAL and IOL. As reported in our previous work, 2 mmol of citral can be completely solubilized into 8 MPa CO₂ in the presence of 4 MPa H₂ at 80 °C [31, 32]. The initial increase of conversion is attributed to the increase of substrate concentration in scCO₂ phase and the elimination of the phase transfer resistance at 8 MPa (homogeneous formed), and the dilution effect might result in the following successive decrease of conversion.

For the monometallic Au/TiO₂ catalyst, the conversion of citral showed a volcano-trend as CO₂ pressure increased, which was similar to the results of the chemically mixed bimetallic catalyst of Au-Pd/TiO₂. The conversion over Au/TiO₂ catalyst reached the maximum at 12 MPa CO₂, which was the same with the case of Au-Pd/TiO₂. However, for Pd/TiO₂ catalyst, the maximum conversion appeared at 8 MPa. With respect to the product distribution, CAL was produced as the main product over the above three catalysts, and the selectivity to CAL increased slightly from 47% to 57% as CO₂ pressure increased. It indicated that the catalytic feature of the bimetallic Pd-Au/TiO₂ catalyst behaved more like Au/TiO₂, as the present Pd-Au/TiO₂ catalyst was surface-rich with Au from the EDS measurement (Figure 4).

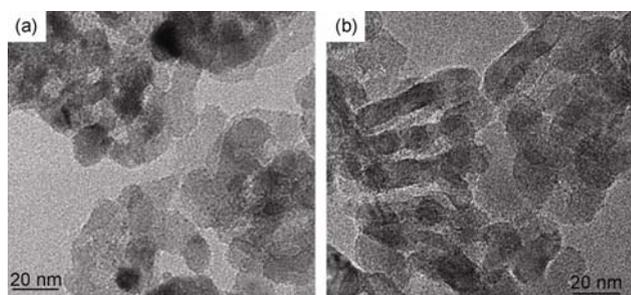


Figure 1 TEM image of bimetallic Au-Pd/TiO₂. (a) The fresh sample; (b) after the second run.

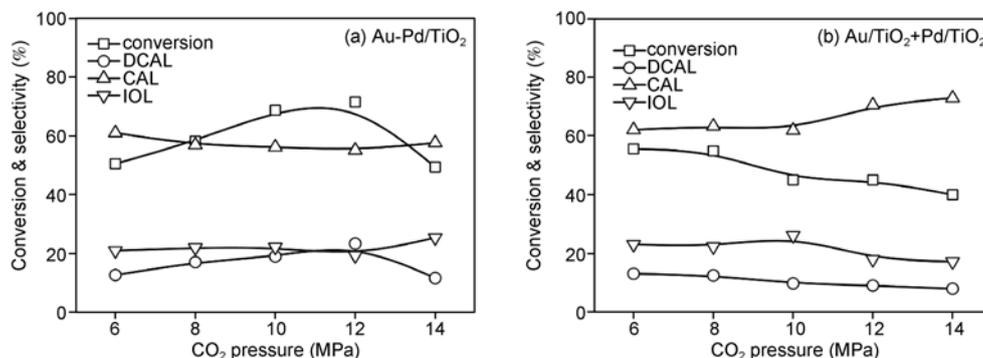


Figure 2 Effect of CO₂ pressure on conversion and selectivity in hydrogenation of citral over (a) bimetallic Pd-Au/TiO₂, (b) physical mixture of Au/TiO₂ and Pd/TiO₂. Reaction conditions: citral 2 mmol, H₂ 4 MPa, 80 °C; (a) Pd-Au/TiO₂ 50 mg, 4 h; (b) Au/TiO₂ 20 mg, Pd/TiO₂ 20 mg, 2 h.

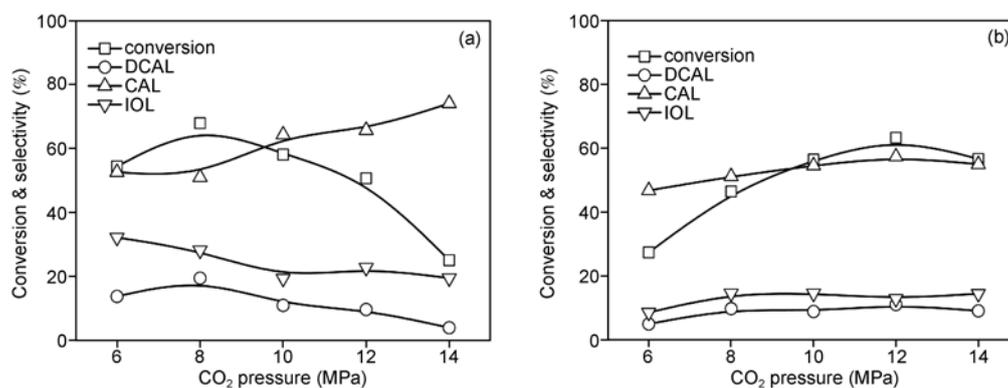


Figure 3 Effect of CO₂ pressure on the conversion and selectivity in hydrogenation of citral over the monometallic Pd/TiO₂ and Au/TiO₂. Reaction conditions: H₂ 4 MPa, 4 h, 80 °C; (a) Pd/TiO₂, citral 2 mmol, catalyst 50 mg; (b) Au/TiO₂, citral 0.6 mmol, catalyst 100 mg.

By contrast, the catalytic performance of the physical mixture of Au/TiO₂ and Pd/TiO₂ was different from bimetallic Pd-Au/TiO₂ catalyst, but it behaved as the simple sum of two monometallic Pd and Au samples from the results of the influence of CO₂ pressure.

The electronic state of supported Au and Pd nanoparticles was assumed to be influenced by CO₂ pressure and then affected the activity, resulting in the maximum conversion appearing at different CO₂ pressures. We have tried to use XPS spectra to analyze the electronic state of Au and Pd nanoparticles supported on TiO₂, however, no signal was observed due to the low metal loading. It was reported that the electron density of gold and silver metal particles decreased with increasing CO₂ pressure in scCO₂ from the shift of the wavelength of their maximum plasmon optical absorption [33, 34]. It was also reported that the electronic state of supported platinum particles could be affected by the scCO₂ solvent in selective hydrogenation of α,β -unsaturated aldehydes over supported platinum catalysts [35, 36], in which the conversion and selectivity to unsaturated alcohols in scCO₂ were higher than those in ethanol and also increased with an increase of CO₂ pressure. The authors claimed that the interaction between metal particles and CO₂ could promote the adsorption of the α,β -unsaturated

aldehydes on the platinum particles with π electrons of their C=O bonds, enhancing the hydrogenation of C=O bonds. The evolution of the product distribution is closely related to the working state of the catalytic systems and the stability of intermediate species on the catalyst surfaces at a particular pressure of CO₂. It was reported that the product distribution of citral hydrogenation strongly depended on CO₂ pressure over micelle-hosted Pd and Ru nanoparticles in scCO₂. The authors pointed out that at lower pressure, although in a supercritical state, the density of the fluid is close to a gas-like phase, and the volatile citral molecules can easily gain access to the catalyst surface and be exhaustively hydrogenated to DCAL before its desorption to the mobile phase. However, at higher pressure, the fluid becomes more liquid-like, enabling solubility of chemical species therein. This enhances desorption of partially hydrogenated intermediate species from the metal surface to the mobile phase [37, 38]. Another example is the hydrogenation of 4-*tert*-butylphenol over Rh/C in scCO₂. As the CO₂ pressure increased, the selectivities to *cis*- and *trans*-4-*tert*-butylcyclohexanol decreased, whereas the selectivity to 4-*tert*-butylcyclohexanone increased due to the higher solubility of the intermediate product 4-*tert*-butylcyclohexene-1-ol at higher CO₂ pressures, resulting in its further hydrogenation to 4-*tert*-butylcyclohexanone [39]. The similar effect also appeared in hydrogenation of naphthalene and tetralin in scCO₂ [40–42]. In addition, the adsorption mode of the reactants on the surface of the catalysts can be tuned through changing CO₂ pressure, resulting in a variation in product distribution. Chatterjee *et al.* [43] reported that compared with ethanol solvent, the scCO₂ medium promoted the selective formation of cyclohexanone (~98%) and the selectivity to cyclohexanone increased as CO₂ pressure increased in the hydrogenation of phenol over palladium supported Al-MCM-41 catalyst. They suggested that scCO₂ is a quadrupolar solvent and the interaction between CO₂ and phenol will be weaker than that for ethanol-phenol with more phenol attracted to the catalyst active site in scCO₂. As a result, phenol was preferred to adsorb on the catalyst

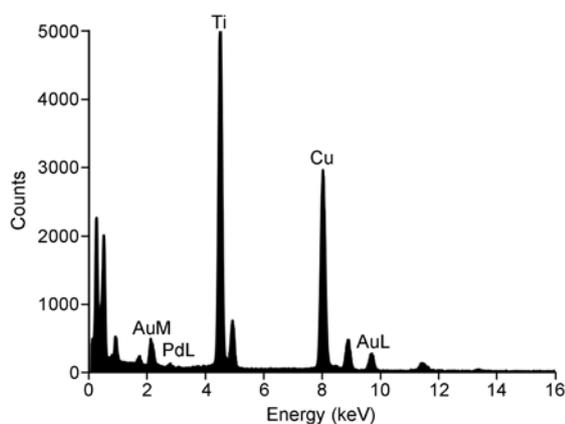


Figure 4 EDS image of the bimetallic Pd-Au/TiO₂ catalyst.

surface in a non-planar way to produce cyclohexanone. It was suggested that the improvement in the product selectivity and reaction rate in scCO_2 was possibly because the CO_2 molecule may act as a modifier on the catalyst surface to block the active sites for a certain reaction step. For example, when hydrogenation of halonitroaromatics was carried out over supported Pt catalysts in scCO_2 , CO generated from CO_2 during the reaction might preferentially cover the active sites for dehalogenation of halonitroaromatics, resulting in a significant increase in halo-aniline selectivity [44]. Recently, Han *et al.* reported that CO_2 could serve as a weak Lewis acid to promote the selectivity of cyclohexanone significantly in the selective hydrogenation of phenol [45]. The true reason for the improvement in selectivity and conversion along with CO_2 pressure is still a debatable issue as mentioned previously, but there is no doubt that the CO_2 pressure has a strong influence, and in most cases the effects are positive as we expected.

The product selectivity was related with conversion, so the changes of product selectivity with conversion over Pd-Au/TiO₂ in the hydrogenation of citral are given in Figure 5. The selectivity to CAL was around 60% at the conversions lower than 70%, and it decreased as the conversion further increased, for that CAL was deeply hydrogenated to DCAL (complete hydrogenation of C=C bonds). For the Pd/TiO₂ catalyst, the selectivity to CAL decreased linearly with the conversion, as the subsequent hydrogenation of CAL was relatively easy on the surface of Pd/TiO₂ [46]. It was reported that DCAL was produced almost in 100% selectivity over the supported Pd catalysts in scCO_2 . Those results indicated that the presence of Au in the bimetallic Pd-Au/TiO₂ catalyst could improve the selectivity of CAL in scCO_2 [47].

4 Conclusions

In summary, it has been demonstrated that significant dif-

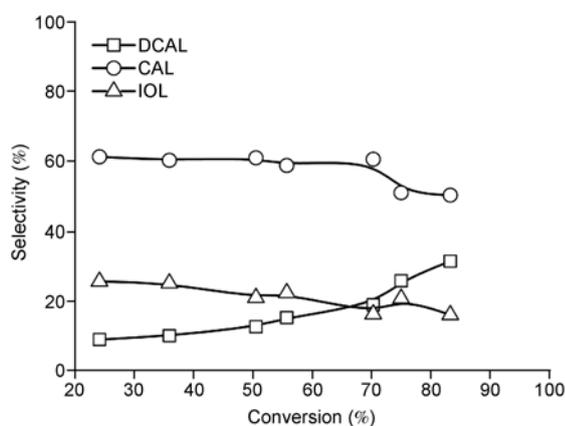


Figure 5 Plots of selectivity against conversion for selective hydrogenation of citral over the bimetallic Pd-Au/TiO₂ catalyst. Reaction condition: citral 2 mmol, Pd-Au/TiO₂, 50 mg, H₂, 4 MPa, CO₂, 8 MPa, 80 °C.

ference in synergistic effect between Au and Pd, Ru appeared in selective hydrogenation of citral in scCO_2 when the physically and chemically mixed TiO₂-supported Pd, Ru, and Au catalysts were used. The catalytic activity increased when Au was mixed with Pd catalyst irrespective of the physical or chemical mix, while the activity was the same when Au was physically mixed with Ru catalyst, but it even disappeared with the chemically mixed Au-Ru/TiO₂ catalyst. The effect of CO_2 pressure on conversion of citral and product selectivity was significantly different for Au/TiO₂, Pd-Au/TiO₂, Pd/TiO₂ and Au/TiO₂+Pd/TiO₂ catalysts, with the maximum conversion appearing at 12 MPa CO₂ for the first two catalysts and at 8 MPa CO₂ for Pd/TiO₂ catalyst, but for the physical mixture of Au/TiO₂+Pd/TiO₂, the conversion decreased slowly with CO₂ pressure. It was assumed that the difference in the interaction of Au, Pd nanoparticles with CO₂ would affect the activity of the catalysts at different CO₂ pressures, which needs further investigation and discussion.

This work was financially supported by the One Hundred Talents Program and YW.H16 from the Chinese Academy of Sciences, the National Natural Science Foundation of China (20573104), and the CAS-JSPS International Joint Project GJHZ05.

- Leitner W. Supercritical carbon dioxide as a green reaction medium for catalysis. *Acc Chem Res*, 2002, 35: 746–756
- Jessop PG, Ikariya T, Noyori R. Homogeneous catalysis in supercritical fluids. *Chem Rev*, 1999, 99: 475–493
- Baiker A. Supercritical fluids in heterogeneous catalysis. *Chem Rev*, 1999, 99: 453–473
- Zhao F, Fujita S, Akihara S, Arai M. Hydrogenation of benzaldehyde and cinnamaldehyde in compressed CO₂ medium with a Pt/C catalyst: A study on molecular interactions and pressure effects. *J Phys Chem A*, 2005, 109: 4419–4424
- Nelson MR, Brokman RF. *Ab initio* calculations on CO₂ binding to carbonyl groups. *J Phys Chem A*, 1998, 102: 7860–7863
- Raveendran P, Wallen SL. Cooperative C···H···O hydrogen bonding in CO₂ Lewis Base complexes: Implications for solvation in supercritical CO₂. *J Am Chem Soc*, 2002, 124: 12590–12599
- Milone C, Ingoglia R, Pistone A, Neri G, Frusteri F, Galvagno S. Selective hydrogenation of α,β -unsaturated ketones to α,β -unsaturated alcohols on gold-supported catalysts. *J Catal*, 2004, 222: 348–356
- Mohr C, Hofmeister H, Radnik J, Claus P. Identification of active sites in gold-catalyzed hydrogenation of acrolein. *J Am Chem Soc*, 2003, 125: 1905–1911
- Okumura M, Akita T, Haruta M. Hydrogenation of 1,3-butadiene and of crotonaldehyde over highly dispersed Au catalysts. *Catal Today*, 2002, 74: 265–269
- Pawelec B, Venezia AM, La Parola V, Cano-Serrano E, Campos-Martin JM, Fierro JLG. AuPd alloy formation in Au-Pd/Al₂O₃ catalysts and its role on aromatics hydrogenation. *Appl Surf Sci*, 2005, 242: 380–391
- Li XL, Li BZ, Cheng MH, Du YK, Wang XM, Yang P. Catalytic hydrogenation of phenyl aldehydes using bimetallic Pt/Pd and Pt/Au nanoparticles stabilized by cubic silsesquioxanes. *J Mol Catal A*, 2008, 284: 1–7
- Pawelec B, Venezia AM, La Parola V, Thomas S, Fierro JLG. Factors influencing selectivity in naphthalene hydrogenation over Au- and Pt-Au-supported catalysts. *Appl Catal A*, 2005, 283: 165–175
- Claus P. Heterogeneously catalyzed hydrogenation using gold catalysts. *Appl Catal A*, 2005, 291: 222–229

- 14 Hammer B, Norskov JK. Why gold is the noblest of all the metals. *Nature*, 1995, 376: 238–240
- 15 Zanella R, Louis C, Giorgio S, Touroude R. Crotonaldehyde hydrogenation by gold supported on TiO₂: Structure sensitivity and mechanism. *J Catal*, 2004, 223: 328–339
- 16 Liu F, Wechsler D, Zhang P. Alloy-structure-dependent electronic behavior and surface properties of Au-Pd nanoparticles. *Chem Phys Lett*, 2008, 461: 254–259
- 17 Cardenas-Lizana F, Gomez-Quero S, Keane M. Gas phase hydrogenation of *m*-dinitrobenzene over alumina supported Au and Au-Ni alloy. *Catal Lett*, 2009, 127: 25–32
- 18 Pawelec B, Cano-Serrano E, Campos-Martin JM, Navarro RM, Thomas S, Fierro JLG. Deep aromatics hydrogenation in the presence of DBT over Au-Pd/gamma-alumina catalysts. *Appl Catal A*, 2004, 275: 127–139
- 19 Venezia AM, La Parola V, Pawelec B, Fierro JLG. Hydrogenation of aromatics over Au-Pd/SiO₂-Al₂O₃ catalysts: Support acidity effect. *Appl Catal A*, 2004, 264: 43–51
- 20 Sarkany A, Geszti O, Safran G. Preparation of Pd-shell-Au-core/SiO₂ catalyst and catalytic activity for acetylene hydrogenation. *Appl Catal OA*, 2008, 350: 157–163
- 21 Sarkany A, Hargittai P, Horvath A. Controlled synthesis of PDDA stabilized Au-Pd bimetallic nanostructures and their activity in hydrogenation of acetylene. *Top Catal*, 2007, 46: 121–128
- 22 Malinowski A. Hydrodechlorination of dichlorodifluoromethane (CFC-12) on silica-supported palladium and palladium-gold catalysts. *Pol J Chem*, 2002, 76: 1461–1466
- 23 Bonarowska M, Pielaszek J, Semikolenov VA, Karpinski Z. Pd-Au/Sibunit carbon catalysts: Characterization and catalytic activity in hydrodechlorination of dichlorodifluoromethane (CFC-12). *J Catal*, 2002, 209: 528–538
- 24 Nutt MO, Heck KN, Alvarez P, Wong MS. Improved Pd-on-Au bimetallic nanoparticle catalysts for aqueous-phase trichloroethene hydrodechlorination. *Appl Catal B*, 2006, 69: 115–125
- 25 Venezia AM, La Parola V, Deganello G, Pawelec B, Fierro JLG. Synergetic effect of gold in Au/Pd catalysts during hydrodesulfurization reactions of model compounds. *J Catal*, 2003, 215: 317–325
- 26 Sarkany A, Horvath A, Beck A. Hydrogenation of acetylene over low loaded Pd and Pd-Au/SiO₂ catalysts. *Appl Catal A*, 2002, 229: 117–125
- 27 Liu R, Yu Y, Yoshida K, Li G, Jiang H, Zhang M, Zhao F, Fujita S, Arai M. Physically and chemically mixed TiO₂-supported Pd and Au catalysts: unexpected synergistic effects on selective hydrogenation of citral in supercritical CO₂. *J Catal*, 2010, 269: 191–200
- 28 Hao J, Xi C, Cheng H, Liu R, Cai S, Arai M, Zhao F. Influence of compressed carbon dioxide on hydrogenation reactions in cyclohexane with a Pd/C catalyst. *Ind Eng Chem Res*, 2008, 47: 6796–6800
- 29 Schwank J. Gold in bimetallic catalysts. *Gold Bull*, 1985, 18: 2–10
- 30 Milone C, Tropeano ML, Gulino G, Neri G, Ingoglia R, Galvagno S. Selective liquid phase hydrogenation of citral on Au/Fe₂O₃ catalysts. *Chem Commun*, 2002, 868–869
- 31 Liu R, Zhao F, Fujita S, Arai M. Selective hydrogenation of citral with transition metal complexes in supercritical carbon dioxide. *Appl Catal A*, 2007, 316: 127–133
- 32 Liu R, Wu C, Wang Q, Ming J, Hao Y, Yu Y, Zhao F. Selective hydrogenation of citral catalyzed with palladium nanoparticles in CO₂-in-water emulsion. *Green Chem*, 2009, 11: 979–985
- 33 Zhao F, Ikushima Y, Shirai M, Ebina T, Arai M. Influence of electronic state and dispersion of supported platinum particles on the conversion and selectivity of selective hydrogenation of α,β -unsaturated aldehyde in supercritical carbon dioxide. *J Mol Catal A*, 2002, 180: 259–265
- 34 Arai M, Nishiyama Y, Ikushima Y. Optical absorption of fine gold particles in supercritical carbon dioxide for the characterization of solvent properties. *J Supercrit Fluid*, 1998, 13: 149–153
- 35 Bhanage BM, Ikushima Y, Shirai M, Arai M. The selective formation of unsaturated alcohols by hydrogenation of α,β -unsaturated aldehydes in supercritical carbon dioxide using unpromoted Pt/Al₂O₃ catalyst. *Catal Lett*, 1999, 62: 175–177
- 36 Zhao F, Ikushima Y, Shirai M, Ebina T, Arai M. Influence of electronic state and dispersion of supported platinum particles on the conversion and selectivity of selective hydrogenation of α,β -unsaturated aldehyde in supercritical carbon dioxide. *J Mol Catal A*, 2002, 180: 259–265
- 37 Meric P, Yu KMK, Kong ATS, Tsang SC. Pressure-dependent product distribution of citral hydrogenation over micelle-hosted Pd and Ru nanoparticles in supercritical carbon dioxide. *J Catal*, 2006, 237: 330–336
- 38 Poliakoff M, Howdle S. Supercritical chemistry: Synthesis with a spanner. *Chem Ber*, 1995, 31: 118–121
- 39 Hiyoshi NV, Rode C, Sato O, Tetsuka H, Shirai M. Stereoselective hydrogenation of tert-butylphenols over charcoal-supported rhodium catalyst in supercritical carbon dioxide solvent. *J Catal*, 2007, 252: 57–68
- 40 Hiyoshi N, Inoue TV, Rode C, Sato O, Shirai M. Tuning *cis*-decalin selectivity in naphthalene hydrogenation over carbon-supported rhodium catalyst under supercritical carbon dioxide. *Catal Lett*, 2006, 106: 133–138
- 41 Hiyoshi N, Mine EV, Rode C, Sato O, Shirai M. Stereoselective hydrogenation of tetralin to *cis*-decalin over a carbon-supported rhodium catalyst in supercritical carbon dioxide solvent. *Chem Lett*, 2006, 35: 188–189
- 42 Hiyoshi N, Mine EV, Rode C, Sato O, Shirai M. Low temperature hydrogenation of tetralin over supported rhodium catalysts in supercritical carbon dioxide solvent. *Appl Catal A*, 2006, 310: 194–198
- 43 Chatterjee M, Kawanami H, Sato M, Chatterjee A, Yokoyama T, Suzuki T. Hydrogenation of phenol in supercritical carbon dioxide catalyzed by palladium supported on Al-MCM-41: A facile route for one-pot cyclohexanone formation. *Adv Synth Catal*, 2009, 351: 1912–1924
- 44 Ichikawa S, Tada M, Iwasawa Y, Ikariya T. The role of carbon dioxide in chemoselective hydrogenation of halonitroaromatics over supported noble metal catalysts in supercritical carbon dioxide. *Chem Commun*, 2005, 924–926
- 45 Liu H, Jiang T, Han B, Liang S, Zhou Y. Selective phenol hydrogenation to cyclohexanone over a dual supported Pd-Lewis acid catalyst. *Science*, 2009, 326: 1250–1252
- 46 Augustine RL. Dekker Inc M, New York, 1996
- 47 Chatterjee M, Chatterjee A, Ikushima Y. Pd-catalyzed completely selective hydrogenation of conjugated and isolated C=C of citral (3,7-dimethyl-2,6-octadienal) in supercritical carbon dioxide. *Green Chem*, 2004, 6: 114–118